

**TORAY**

Toray Composite Materials America, Inc.

# **TORAYCA<sup>®</sup>**

# **Technical Manual**

HIGH PERFORMANCE CARBON FIBER  
**TORAYCA**



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777

Revision 4/2020



Toray Composite Materials America, Inc.

# Contact Information

[www.toraycma.com](http://www.toraycma.com)

**TORAY CMA HEAD OFFICE & TACOMA PLANT**

19002 50<sup>th</sup> Ave. E, Tacoma, Washington 98446

TEL: 1-800-208-6729

TEL: 1-253-846-1777

FAX: 1-253-846-3897

**DECATUR PLANT & CARBON FIBER TECHNICAL CENTER**

2030 Highway 20, P. O. Box 248, Decatur, Alabama 35601

TEL: 1-256-260-2626

FAX: 1-256-260-2627

**SPARTANBURG PLANT**

2202 Moore-Duncan Highway, Moore, SC 29369

TEL: 1-864-586-3444

FAX: 1-864586-3517

**CARBON FIBER SALES OFFICE**

700 Parker Square, Suite 275, Flower Mound, Texas 75028

TEL: 1-972-899-2930

FAX: 1-972-899-2938

**AEROSPACE & GENERAL AVIATION MARKET SALES**

TEL: (253) 846-3109

FAX: (253) 875-1317

**SPORTING GOODS SALES**

TEL: (253) 875-1312

FAX: (253) 875-1317



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# Table of Contents

## 1. GENERAL INFORMATION

<b>TORAYCA®</b> Carbon Fiber .....	1
Fiber Selection Guide .....	2
<b>TORAYCA®</b> Carbon Fiber Properties .....	5
Explanation of Product Code .....	7
Quality Policy & Assurance .....	10
Safety & Handling .....	13
Disclosure .....	14

## 2. TORAYCA® DATA SHEETS

T300.....	16
T700S .....	18
T700G.....	20
T800H.....	22
T800S .....	24
T1000G.....	26
T1100S .....	27
T1100G.....	28
M35J .....	30
M40J .....	32
M46J .....	34
M55J .....	36
M60J .....	38



www.toraycma.com  
1-253-846-1777

**TORAY**

Toray Composite Materials America, Inc.

# TORAYCA<sup>®</sup> CARBON FIBER

**Toray Industries, Inc.**, of Japan has been the worldwide leader in the development and production of carbon fibers for over 40 years. Trade named **TORAYCA<sup>®</sup>**, our carbon fibers represent the most complete selection available in the global market, with the highest standards of quality and performance.

**TORAYCA<sup>®</sup>** fiber is developed at our **Ehime** manufacturing complex in Japan – Toray’s primary center for carbon fiber and composite technology. In addition to Japan, **TORAYCA<sup>®</sup>** fiber is produced in the United States, France and South Korea. Global capacity is currently at 29,100 metric tons per year.

Toray is the world leader in carbon fiber technology as well as in production capacity:

- Largest carbon fiber manufacturer in the world
- Widest range and largest variety of carbon fiber
- World’s first commercial manufacturer of PAN based carbon fibers, since 1971
- Global carbon fiber manufacturing/operation (Japan, U.S., Europe, South Korea)
- One of the top patent holders in the field of carbon fiber/composites
- Most comprehensive technical support
- Highest quality carbon fiber products
- Continued investment in and expansion of R&D activities.

HIGH-PERFORMANCE CARBON FIBER  
**TORAYCA**



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# FIBER SELECTION GUIDE

**TORAYCA**<sup>®</sup> carbon fibers, produced in a wide range of material properties, are specifically designed to meet your diverse and challenging applications.

This carbon fiber selection guide is helpful in determining which type of carbon fiber is suited to a particular application. **TORAYCA**<sup>®</sup> is grouped into two main categories, **T** series and **M** series. The **T** series has high strength carbon fibers with both regular and intermediate modulus values. The **M** series has more intermediate and high modulus carbon fibers as well as enhanced, higher strength **MJ** type fibers.

To assist you in the selection of the correct **TORAYCA**<sup>®</sup> carbon fiber to meet a specific application, contact our Sales and Technical team.

---

## **FIBER SELECTION GUIDE** (Tensile Strength, Tensile Modulus)

### **T300** (512 ksi, 33.4 Msi)

Baseline carbon fiber used in aerospace applications with over 20 year service history. Has 30 year production history and is known for balanced composite properties, high quality and consistency, reliability and availability of supply. Available in 1K, 3K, 6K and 12K tow sizes.

### **T700S** (711 ksi, 33.4 Msi)

An industry standard fiber for high strength and standard modulus, with outstanding processing characteristics for filament winding, weaving and prepregging. This never-twisted fiber is used in a variety of industrial and recreational applications, including pressure vessels such as natural gas vehicle (NGV) storage tanks and SCBA breathing tanks. Available in 6K, 12K, and 24K tow sizes.

### **T700G** (711 ksi, 34.8 Msi)

Enhanced tensile modulus and adhesion properties over T700S. Applications of this never-twisted fiber include aircraft and high performance sporting goods where demanding conditions require superior composite properties. Available in 12K tow sizes.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

## FIBER SELECTION GUIDE

### **T800H** (796 ksi, 42.7 Msi)

An intermediate modulus, high tensile strength fiber, with high level and balance of composite properties. Designed and developed to meet the weight saving demands of aircraft applications. Is used in primary structure of commercial aircraft, including vertical fin and horizontal stabilizers. Available in 6K and 12K tow sizes.

### **T830H** (774 ksi, 42.7 Msi)

An intermediate modulus, high tensile strength fiber with a good balance of composite properties. Is used extensively in aircraft secondary structures. Available in a 6K tow size.

### **T800S** (853 ksi, 42.7 Msi)

A cost-effective intermediate modulus fiber with higher tensile strength compared to T800H. This never-twisted fiber has especially high tensile properties. Is used extensively in primary structure of commercial aircraft. Available in 12K and 24K tow sizes.

### **T1000G** (924 ksi, 42.7 Msi)

A very high tensile strength carbon fiber. Suitable for lightweight, tensile strength-critical applications such as pressure vessels for aerospace vehicles and satellites as well as hydrogen storage tanks for fuel cell vehicles. Available in a 12K tow size.

### **T1100S** (1,017 ksi, 47.0 Msi)

Next-generation intermediate modulus fiber with excellent processability and enhanced performance in demanding manufacturing methods such as filament winding. Available in a 12K and 24K tow sizes.

### **T1100G** (1,017 ksi, 47.0 Msi)

Next-generation intermediate modulus fiber with excellent processability in high-performance manufacturing methods such as weaving, prepreg, etc. Available in a 12K and 24K tow sizes.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# FIBER SELECTION GUIDE

**MJ** type fibers have enhanced tensile strength and modulus. These fibers are usually selected for a specific modulus that is used for stiffness, coefficient of thermal expansion (CTE), and electrical and thermal conductivity for spacecraft and premium sporting goods. The chart below lists the typical properties of the fibers only.

Fiber Type	Tensile Strength (ksi)	Tensile Modulus (Msi)	CTE ( $\alpha \cdot 10^{-6}/^{\circ}\text{C}$ )	Electrical Resistivity ( $10^{-3} \Omega \cdot \text{cm}$ )	Thermal Conductivity ( $\text{Cal}/\text{cm} \cdot \text{s} \cdot ^{\circ}\text{C}$ )
<b>M35J</b>	654 (6K) 683 (12K)	49.8	-0.73	1.1	0.0933
<b>M40J</b>	640	54.7	-0.83	1.0	0.164
<b>M46J</b>	609 (6K) 583 (12K)	63.3	-0.9	0.9	0.202
<b>M50J</b>	597	69.0	-1.0	0.9	0.234
<b>M55J</b>	583	78.2	-1.1	0.8	0.372
<b>M60J</b>	554	85.3	-1.1	0.7	0.363



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# TORAYCA® CARBON FIBER PROPERTIES

**TORAYCA® TYPICAL FIBER PROPERTIES (Nominal Values)**

FIBER TYPE		Number of Filaments	Sizing Type	Tensile Strength*		Tensile Modulus*		Elongation %	Yield g/1000m	Density g/cm <sup>3</sup>	Standard Spool Size** (kg)
				ksi	MPa	Msi	GPa				
STANDARD MODULUS	T300	1,000	4,5	512	3,530	33.4	230	1.5	66	1.76	1.0
		3,000	4,5						198		2.0
		6,000	4,5						396		2.0
	T700S	6,000	5	711	4,900	33.4	230	2.1	396	1.80	2.0
		12,000	5,6,F						800		4.0, 6.0, 8.0
		24,000	5,6,F						1,650		6.0, 8.0
T700G	12,000	3,4,5	711	4,900	34.8	240	2.0	800	1.80	6.0	
INTERMEDIATE MODULUS	T800H	6,000	4	796	5,490	42.7	294	1.9	223	1.81	2.0
		12,000	4,5						445		4.0
	T830H	6,000	4	774	5,340	42.7	294	1.8	223	1.81	2.0
	T800S	12,000	5	853	5,880	42.7	294	2.0	515	1.80	4.0
		24,000	1						1,030		4.0
	T1000G	12,000	4	924	6,370	42.7	294	2.2	485	1.80	4.0
	T1100G	12,000	7	1,017	7,000	47.0	324	2.0	505	1.79	2.0
		24,000	7						1,010		4.0
	T1100S	12,000	5	1,017	7,000	47.0	324	2.0	505	1.79	2.0
		24,000	5						1,010		4.0
HIGH MODULUS	M35J	6,000	5	654	4,510	49.8	343	1.3	225	1.75	1.0
		12,000	5	683	4,700			1.4	450		2.0
	M40J	6,000	5	640	4,400	54.7	377	1.2	225	1.77	1.0
		12,000	5						450		2.0
	M46J	6,000	5	609	4,200	63.3	436	1.0	223	1.84	1.0
		12,000	5	583	4,020			0.9	445		2.0
	M55J	6,000	5	583	4,020	78.2	540	0.8	218	1.91	0.5
	M60J	3,000	5	554	3,820	85.3	588	0.7	103	1.93	0.25
		6,000	5						206		0.4

\*Measured using the impregnated strand method. This information can be used for material selection purposes only.

\*\*Other sizes available, refer to product data sheet.




www.toraycma.com  
1-253-846-1777



Toray Composite Materials America, Inc.

# TORAYCA® CARBON FIBER PROPERTIES

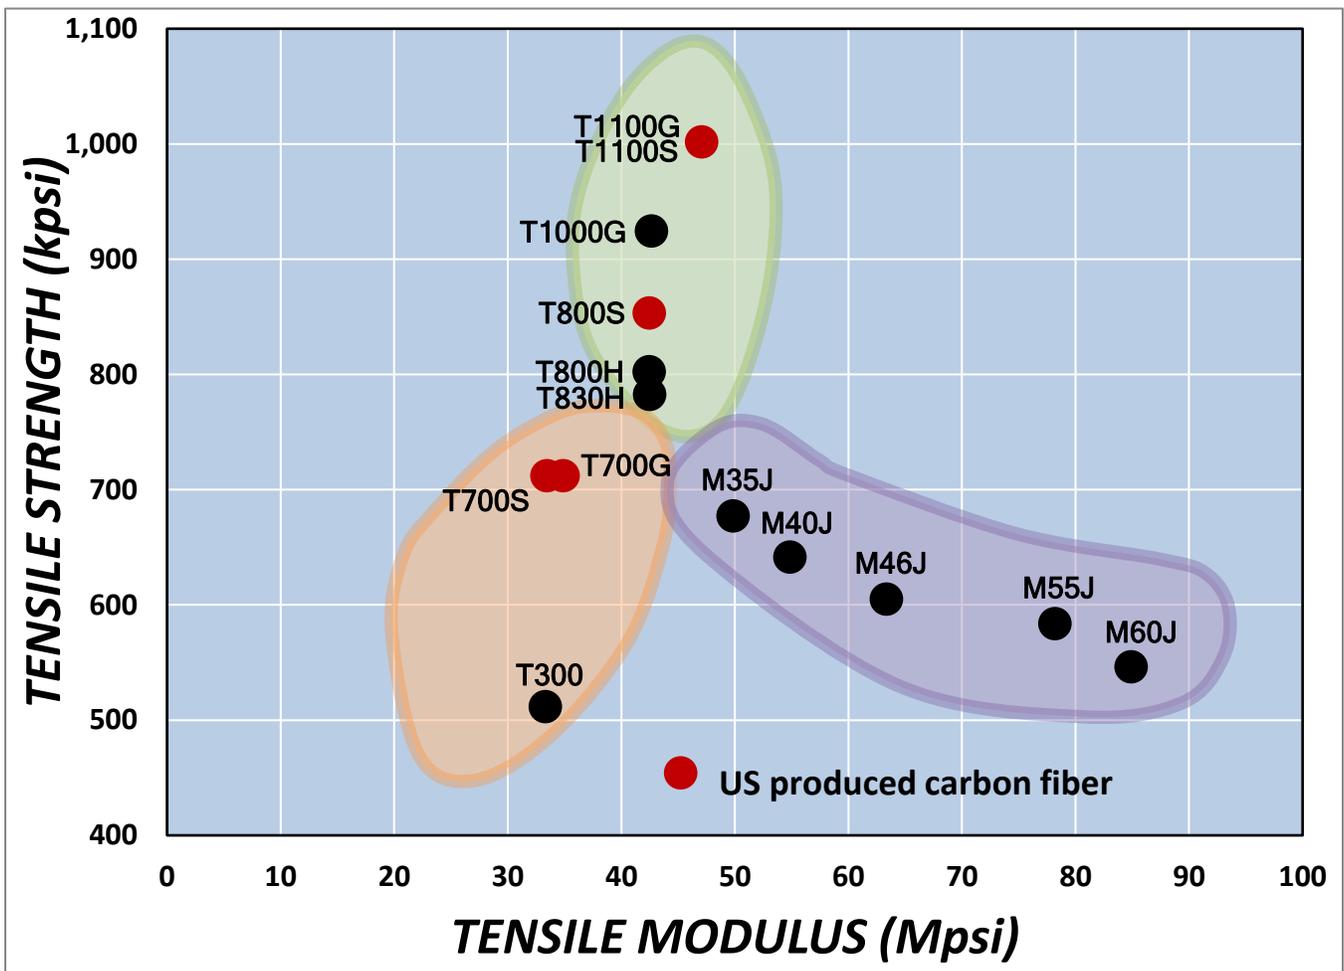


[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# EXPLANATION OF PRODUCT CODE

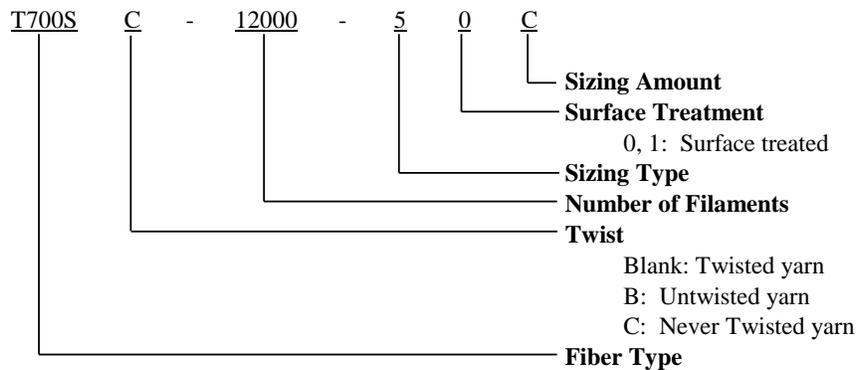

## FIBER TYPE

**T700S**C – 24000 – 50C

Currently, **TORAYCA**<sup>®</sup> fibers are separated into two main series: **T** and **M**. The **T** series stands for tensile strength, while the **M** series indicates modulus. Included in the **M** series are **MJ** type fibers, which have enhanced tensile and compressive strength properties over first generation **M** series fibers.

Originally, in the **T** series, the three- or four-digit number designated the approximate tensile strength in either kg<sub>f</sub>/mm<sup>2</sup> or kpsi. For example, T700S has a tensile strength of 711 kpsi.

In the case of **M** series fibers, the two-digit number designates the approximate modulus in SI units. For example, M55J has a tensile modulus of 55x10<sup>3</sup> kg<sub>f</sub>/mm<sup>2</sup>.

The specific properties of each type of fiber can be found on the selection guide sheets, along with the individual data sheets.



www.toraycma.com  
1-253-846-1777



Toray Composite Materials America, Inc.

# EXPLANATION OF PRODUCT CODE

**TWIST** T700SC – 24000 – 50C

Originally, **TORAYCA**<sup>®</sup> fibers were produced as twisted fibers. Because of other application requirements, **TORAYCA**<sup>®</sup> is also produced as untwisted and never twisted fiber. Twist of the fiber is designated as follows:

- (No letter) Twisted Fiber
- B Untwisted Fiber (made from a twisted fiber tow through an untwisting process)
- C Never Twisted Fiber

Please see the individual data sheets for fiber twist of each product.

**TOW SIZE** T700SC – 24000 – 50C

Tow sizes, or number of carbon fiber filaments per tow, vary from 1000 to 48000 filaments. **TORAYCA**<sup>®</sup> fibers are available in specific tow size for each product. Consult the data sheets for available tow sizes.

**SIZING** T700SC – 24000 – 50C

**TORAYCA**<sup>®</sup> fibers are treated with various sizing agents to enhance the handleability and bonding characteristics with various resin systems. Below are the sizing types developed for **TORAYCA**<sup>®</sup> fibers. Not all sizings are available with every fiber. Please see the data sheets for available sizings of a particular fiber.

Sizing Type	Resin System Compatibility
1	Epoxy
3	Epoxy
4	Epoxy, Phenolic, BMI
5	General Purpose: Epoxy, Phenolic, Polyester, Vinyl Ester
6	Epoxy
7	Epoxy
F	Vinyl Ester, Epoxy



www.toraycma.com  
1-253-846-1777



Toray Composite Materials America, Inc.

# EXPLANATION OF PRODUCT CODE

## ***SURFACE TREATMENT***

T700SC – 24000 – 50C

**TORAYCA**<sup>®</sup> fibers are surface treated to enhance the adhesion properties with resin systems in a process known as oxidation. Oxygen atoms are chemically added to the surface of the fiber to increase the bonding characteristics.

The surface treatment is designated as follows:

0, 1    Surface treated

## ***SIZING AMOUNT***

T700SC – 24000 – 50C

To control the handleability and adhesion properties, various amounts of sizing are applied to **TORAYCA**<sup>®</sup> fibers. The sizing amount is designated as a letter (A to E) for a specific fiber. Because of various applications, the letter may correspond to different sizing amounts from fiber type to fiber type. See the fiber data sheet for specific sizing amounts.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# QUALITY POLICY & ASSURANCE

## **QUALITY POLICY**

Toray Composite Materials America, Inc. will strive to provide the highest quality, innovative technology, and products that meet our customer, statutory, and regulatory requirements with emphasis on continuous process improvements through employee involvement.

## **QUALITY CONTROL AND ASSURANCE**

A stringent integrated quality control system established for manufacturing, inspection, storage and delivery procedures has resulted in the very high quality of **TORAYCA®** products.

These quality standards are the inherited experience of Toray's synthetic fiber manufacturing processes for the past 80 plus years. This dedicated quality control system has been certified by today's aerospace manufacturers and has resulted in our Decatur, Alabama CMA facility achieving Nadcap certification in 2017. Certifications at CMA in Alabama for manufacture of Carbon Fibers are ISO 9000 certified in 2000, and was upgraded to AS 9100 in 2003. Pan fiber certification at Alabama CMA is ISO 9001 in 2008. The plant also became ISO 14001 certified in 2008.

**TORAYCA®** and to state the lot average values for tensile strength, tensile modulus, an ultimate strain at failure, density, yield, and sizing amount. These values are tested in accordance with Toray Test Methods. A copy of these Test Methods will be provided upon request.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# QUALITY POLICY & ASSURANCE

**TORAYCA**<sup>®</sup> carbon fiber is identified by labels attached to the Case and to the Bobbin. Examples of bobbin labels from CMA and Toray Industries are shown below.



Manufacturing records of a particular **TORAYCA**<sup>®</sup> carbon fiber product are easily traceable through Lot and Case numbers. Therefore, the Lot, Trace, and Case numbers are critical to the tracking of specific **TORAYCA**<sup>®</sup> product history. Every bobbin produced has full traceability.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777




Toray Composite Materials America, Inc.

# QUALITY POLICY & ASSURANCE

The product designation is described in the Explanation of Product Code section.

The lot number contains the following information.

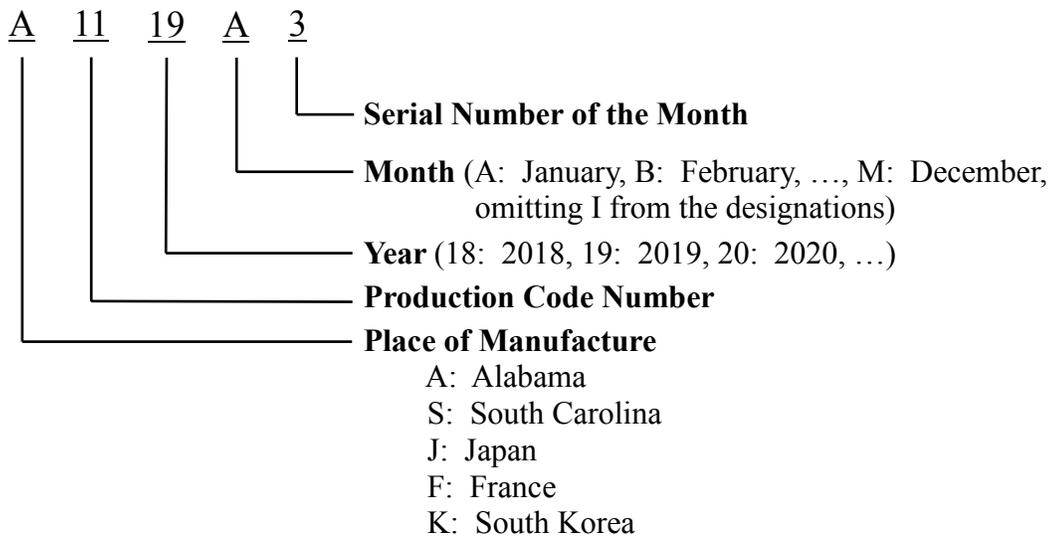

[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# SAFETY & HANDLING

Carbon fibers are composed of thin single filaments, whose diameter is in the range of 5 to 7 micrometers. During processing, these single filaments can be damaged, causing dust and broken filaments to arise which may cause potential hazards such as:

- Skin irritation and dermatitis
- Electrical hazards (Carbon fiber is electrically conductive.)
- Respiratory problems

The following safety and handling guidelines should be followed at all times to protect workers and electrical devices:

- Be sure to read through the Safety Data Sheet (SDS) before handling carbon fiber.
- Personnel should wear goggles, facemasks, gloves and protective clothing wherever dust generation is significant.
- Personal cleanliness and careful work habits are positive preventive actions.
- Rotary bars and rollers are preferred to guide fiber tows instead of stationary eye guides, pins, or bars.
- Local removal of dust at the point of generation is highly effective.
- Electrical equipment should be isolated. Protecting expensive computer systems with complete encasement and fresh air purge is highly recommended.
- Routine tests of particle concentration are recommended.
- Do not incinerate carbon fiber. Waste fibers should be packaged for burial in landfill authorized for the disposal of special waste of this nature, following local, state, and federal regulations as appropriate.
- Additional Safety & Handling information is printed on the cardboard cases.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# DISCLOSURE

We believe the information in this **TORAYCA**<sup>®</sup> Technical Manual is correct to the best of our current knowledge. However, no warranty is made with respect to its completeness.

This manual does not anticipate all the situations in which this material is processed or all the physical and mental characteristics of each individual who is involved in the processing. It is the user's obligation to test and use material safely in accordance with every relevant regulation and law. Unless otherwise agreed in writing, no liability is assumed by Toray Industries of Japan or Toray Composite Materials America, Inc. for any claims or damages caused in relation to the use of this material.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# DATA SHEETS

Additional carbon fiber properties and packaging information are listed on the following individual data sheets for each **TORAYCA**<sup>®</sup> fiber.

All values noted on these data sheets are typical properties and do not constitute any guarantee of values or warranty of any kind. These values are intended to be a general guideline for material selection purposes only. For applications requiring guaranteed values, contact our sales and technical team to establish a material specification document.



[www.toraycma.com](http://www.toraycma.com)  
1-253-846-1777



Toray Composite Materials America, Inc.

# T300

## STANDARD MODULUS CARBON FIBER

Baseline carbon fiber with a 40-year production history and is known for its balanced composite properties, high quality, consistency, reliability and suppliability. Excellent processability in traditional manufacturing methods (weaving, braiding, filament winding, prepreg, etc). Manufacturing locations include Japan and France.

### PRODUCT DESIGNATION

T300	B	3,000	4	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* Blank: Twisted  
B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	512 ksi	3,530 MPa	TY-030B-01
Tensile Modulus	33.4 Msi	230 GPa	TY-030B-01
Strain at Failure		1.5%	TY-030B-01
Density		1.76 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		7 μm	
Yield	1K	66 g/1000m	TY-030B-03
	3K	198 g/1000m	TY-030B-03
	6K	396 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.41 α · 10 <sup>-6</sup> /°C
Specific Heat	0.777 J/g · °C
Thermal Conductivity	0.105 J/cm · s · °C
Electric Resistivity	1.7 × 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>93%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
40A/B (1.0%)	Epoxy	TY-030B-05
40D (0.7%)	Epoxy	TY-030B-05
50A/B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	264 ksi	1,820 MPa	ASTM D-3039
Tensile Modulus*	20 Msi	140 GPa	ASTM D-3039
Tensile Strain		1.26%	ASTM D-3039
Compressive Strength*	213 ksi	1,470 MPa	SACMASRM1R-94
Flexural Strength*	260 ksi	1,790 MPa	ASTM D-790
Flexural Modulus*	18 Msi	123 GPa	ASTM D-790
ILSS	14 ksi	94.1 MPa	SACMASRM1R-94
In Plain Shear Strength	14 ksi	95 MPa	ASTM D-3518
90° Tensile Strength	11 ksi	76 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.



# T300

T300 Rev. 6: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
1K	1.0	II	76	82	192	132	156	12	12
3K	2.0	II	76	82	192	157	156	12	24
6K									

**Bobbin Type:**

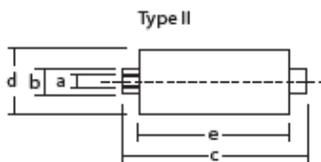

*Please refer to SDS for handling and disposal.*

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777



Toray Composite Materials America, Inc.

# T700S

## STANDARD MODULUS CARBON FIBER

Excellent processability in traditional manufacturing methods (weaving, braiding, filament winding, prepreg, etc). Manufacturing locations include Japan, U.S., Korea, and France.

### PRODUCT DESIGNATION

T700S	C	12,000	5	0	C
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* C: Never Twisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	711 ksi	4,900 MPa	TY-030B-01
Tensile Modulus	33.4 Msi	230 GPa	TY-030B-01
Strain at Failure		2.1%	TY-030B-01
Density		1.80 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		7 μm	
Yield	6K	400 g/1000m	TY-030B-03
	12K	800 g/1000m	TY-030B-03
	24K	1,650 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.38 α · 10 <sup>-6</sup> /°C
Specific Heat	0.752 J/g · °C
Thermal Conductivity	0.0938 J/cm · s · °C
Electric Resistivity	1.6 x 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>93 %
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50C (1.0 %)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05
60E (0.3 %)	Epoxy	TY-030B-05
F0E (0.7 %)	Vinyl ester, compatible with epoxy	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	415 ksi	2,860 MPa	ASTM D-3039
Tensile Modulus*	19 Msi	134 GPa	ASTM D-3039
Tensile Strain		2.02%	ASTM D-3039
Compressive Strength*	210 ksi	1,450 MPa	SACMASRM1R-94
Flexural Strength*	245 ksi	1,690 MPa	ASTM D-790
Flexural Modulus*	17 Msi	120 GPa	ASTM D-790
ILSS	13 ksi	86.9 MPa	SACMASRM1R-94
In Plain Shear Strength	20 ksi	136 MPa	ASTM D-3518
90° Tensile Strength	12 ksi	81 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2592 epoxy at 130 °C.



## T700S

T700S Rev. 4: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	SIZING	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
				a	b	c	d	e		
6K	50C	2.0	III	76.5	82.5	280	130	252	12	24
12K/24K	50C/60E/F0E	6.0	III	76.5	82.5	280	190	252	4	24

**Bobbin Type:**

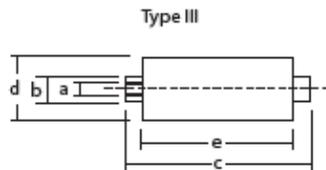

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

T700S Rev. 4: Updated April 13, 2018



Toray Composite Materials America, Inc.

# T700G

## STANDARD MODULUS CARBON FIBER

Enhanced tensile modulus with excellent processability in traditional manufacturing methods (weaving, braiding, filament winding, prepreg, etc). Manufacturing locations include Japan, U.S., and France.

### PRODUCT DESIGNATION

T700G	C	12,000	3	1	E
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* C: Never twisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	711 ksi	4,900 MPa	TY-030B-01
Tensile Modulus	34.8 Msi	240 GPa	TY-030B-01
Strain at Failure		2.0%	TY-030B-01
Density		1.80 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		7 μm	
Yield	12K	800 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.3 α · 10 <sup>-4</sup> /°C
Specific Heat	0.752 J/g · °C
Thermal Conductivity	0.096 J/cm · s · °C
Electric Resistivity	1.5 × 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>95%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
31E (0.5%)	Epoxy	TY-030B-05
41E (0.5%)	Epoxy	TY-030B-05
51C (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	296 ksi	2,040 MPa	ASTM D-3039
Tensile Modulus*	20 Msi	141 GPa	ASTM D-3039
Tensile Strain		1.40%	ASTM D-3039
Compressive Strength*	239 ksi	1,645 MPa	SACMASRM1R-94
Flexural Strength*	286 ksi	1,970 MPa	ASTM D-790
Flexural Modulus*	18 Msi	125 GPa	ASTM D-790
ILSS	15 ksi	102.1 MPa	SACMASRM1R-94
In Plain Shear Strength	19 ksi	128 MPa	ASTM D-3518
90° Tensile Strength	11 ksi	75 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.



## T700G

T700G Rev. 5: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
12K	6.0	III	76.5	82.5	280	200	252	4	24

**Bobbin Type:**

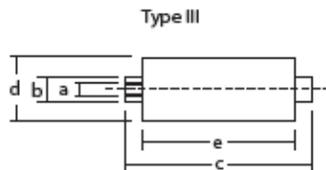

*Please refer to SDS for handling and disposal.*

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.

T700G Rev. 5: Updated April 13, 2018



Toray Composite Materials America, Inc.

# T800H

## INTERMEDIATE MODULUS CARBON FIBER

Intermediate modulus, high tensile strength fiber, with excellent balanced composite properties. Designed and developed to meet the weight saving demand of aircraft. Excellent processability in traditional manufacturing methods (weaving, braiding, filament winding, prepreg, etc). Manufacturing locations include Japan and France.

### PRODUCT DESIGNATION

T800H	B	12,000	4	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	796 ksi	5,490 MPa	TY-030B-01
Tensile Modulus	42.7 Msi	294 GPa	TY-030B-01
Strain at Failure		1.9%	TY-030B-01
Density		1.81 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	223 g/1000m	TY-030B-03
	12K	445 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.56 α · 10 <sup>-6</sup> /°C
Specific Heat	0.752 J/g · °C
Thermal Conductivity	0.10 J/cm · s · °C
Electric Resistivity	1.4 x 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>96%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
40B (1.0%)	Epoxy	TY-030B-05
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	424 ksi	2,920 MPa	ASTM D-3039
Tensile Modulus*	24 Msi	168 GPa	ASTM D-3039
Tensile Strain		1.67%	ASTM D-3039
Compressive Strength*	225 ksi	1,550 MPa	SACMASRM1R-94
Flexural Strength*	248 ksi	1,710 MPa	ASTM D-790
Flexural Modulus*	21 Msi	147 GPa	ASTM D-790
ILSS	13 ksi	88.5 MPa	SACMASRM1R-94
In Plain Shear Strength	24 ksi	164 MPa	ASTM D-3518
90° Tensile Strength	14 ksi	97 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2592 epoxy at 130 °C.



## T800H

T800H Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

### PACKAGING

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	2.0	II	76	82	192	157	156	12	24
12K	4.0	III	76.5	82.5	280	166	252	6	24

### Bobbin Type:

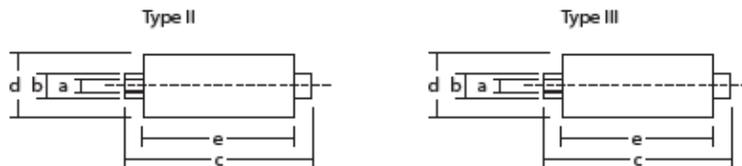

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

T800H Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# T800S

## INTERMEDIATE MODULUS CARBON FIBER

Intermediate modulus, high tensile strength fiber, developed as a cost effective alternative to T800H. This never twisted fiber has excellent tensile composite properties and is specifically designed to meet the weight saving demand of aircraft and high performance recreational products. Excellent processability in traditional manufacturing methods (weaving, braiding, filament winding, prepreg, etc). Manufacturing locations include Japan, US, and France.

### PRODUCT DESIGNATION

T800S	C	24,000	1	0	E
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* C: Nevertwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	853 ksi	5,880 MPa	TY-030B-01
Tensile Modulus	42.7 Msi	294 GPa	TY-030B-01
Strain at Failure		2.0%	TY-030B-01
Density		1.80 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	12K	515 g/1000m	TY-030B-03
	24K	1,030 g /1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.4 α ·10 <sup>-6</sup> /°C
Specific Heat	0.740 J/g ·°C
Thermal Conductivity	0.113 J/cm ·s·°C
Electric Resistivity	1.3 x 10 <sup>3</sup> Ω·cm
Chemical Composition: Carbon	>96%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
10E (0.5%)	Epoxy	TY-030B-05
50C (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	477 ksi	3,290 MPa	ASTM D-3039
Tensile Modulus*	24 Msi	163 GPa	ASTM D-3039
Tensile Strain		1.94%	ASTM D-3039
Compressive Strength*	216 ksi	1,490 MPa	SACMASRM 1R-94
Flexural Strength*	247 ksi	1,700 MPa	ASTM D-790
Flexural Modulus*	21 Msi	145 GPa	ASTM D-790
ILSS	13 ksi	87.9 MPa	SACMASRM 1R-94
In Plain Shear Strength	20 ksi	135 MPa	ASTM D-3518
90° Tensile Strength	11 ksi	79 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2592 epoxy at 130 °C.



## T800S

T800S Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

### PACKAGING

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	SIZING	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
				a	b	c	d	e		
12K	50C	4.0	III	76.5	82.5	280	160	252	6	24
24K	10E	7.8	III	76.5	82.5	280	198	252	4	31.2

#### Bobbin Type:

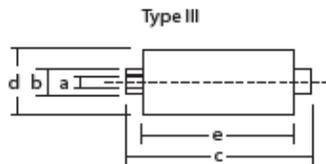

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

T800S Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# T1000G

## INTERMEDIATE MODULUS CARBON FIBER

Legacy intermediate modulus fiber with excellent processability in traditional manufacturing methods (filament winding). Manufactured in Japan.

### PRODUCT DESIGNATION

T1000G	C	12,000	4	0	D
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\*C: Never Twisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	924 ksi	6,370 MPa	TY-030B-01
Tensile Modulus	43.0 Msi	294 GPa	TY-030B-01
Strain at Failure		2.2%	TY-030B-01
Density		1.80 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	12K	485 g/1000m	TY-030B-03

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
40D (0.7%)	Epoxy	TY-030B-05

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.6 α · 10 <sup>-6</sup> /°C
Specific Heat	0.752 J/g · °C
Thermal Conductivity	0.105 J/cm · s · °C
Electric Resistivity	1.4 × 10 <sup>3</sup> Ω · cm
Chemical Composition: Carbon	>95%
Na + K	<50 ppm


### PACKAGING

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
12K	2.0	III	76.5	82.5	280	140	252	12	24

### Bobbin Type:

Type III

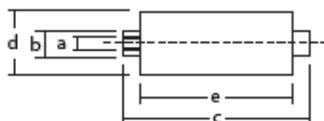

## T1000G

T1000G Rev.0: Updated January 17, 2018



www.toraycma.com  
253-846-1777



Toray Composite Materials America, Inc.

# T1100S

## INTERMEDIATE MODULUS CARBON FIBER

Next-generation intermediate modulus fiber with excellent processability in traditional manufacturing methods (filament winding). Manufactured in the U.S.

### PRODUCT DESIGNATION

T1100S	C	12,000	7	1	E
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\*C: Never Twisted

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50C (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### FIBER PROPERTIES


PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	1,017 ksi	7,000 MPa	TY-030B-01
Tensile Modulus	47.0 Msi	324 GPa	TY-030B-01
Strain at Failure		2.0%	TY-030B-01
Density		1.79 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	12K	505 g/1000m	TY-030B-03

### PACKAGING

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
12K	2.0	III	76.5	82.5	280	125	252	12	24

### Bobbin Type:

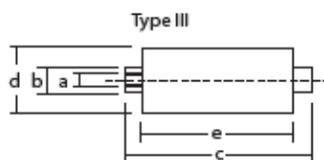

T1100S

T1100S Rev. 1: Updated April 4, 2018



www.toraycma.com  
253-846-1777



Toray Composite Materials America, Inc.

# T1100G

## INTERMEDIATE MODULUS CARBON FIBER

Next-generation intermediate modulus fiber with excellent processability in traditional manufacturing methods (weaving, prepreg, etc). Manufactured in the U.S.

### PRODUCT DESIGNATION

T1100G	C	12,000	7	1	E
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\*C: Never Twisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	1,017 kpsi	7,000 MPa	TY-030B-01
Tensile Modulus	47.0 Mpsi	324 GPa	TY-030B-01
Strain at Failure		2.0%	TY-030B-01
Density		1.79 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	12K	505 g/1000m	TY-030B-03
	24K	1,010 g /1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.5 α · 10 <sup>-6</sup> /°C
Specific Heat	0.748 J/g · °C
Thermal Conductivity	0.130 J/cm · s · °C
Electric Resistivity	1.4 x 10 <sup>-3</sup> Ω·cm
Chemical Composition: Carbon	>96%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
71E (0.6%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	502 Ksi	3,460 MPa	ASTM D-3039
Tensile Modulus*	27 Msi	185 GPa	ASTM D-3039
Tensile Strain		1.82%	ASTM D-3039
Compressive Strength*	271 Ksi	1,870 MPa	SACMASRM1R-94
Flexural Strength*	278 Ksi	1,920 MPa	ASTM D-790
Flexural Modulus*	23 Msi	159 GPa	ASTM D-790
ILSS	15 Ksi	104.5 MPa	SACMASRM1R-94
In Plain Shear Strength	23 Ksi	160 MPa	ASTM D-3518
90° Tensile Strength	12 Ksi	80 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2574 epoxy at 130 °C.



# T1100G

T1100G Rev.1: Updated April 13, 2018



www.toraycma.com  
253-846-1777


**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
12K	2.0	III	76.5	82.5	280	125	252	12	24
24K	4.0	III	76.5	82.5	280	160	252	6	24

**Bobbin Type:**

Type III

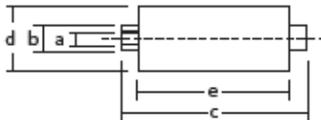

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

T1100G Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# M35J

## HIGH MODULUS CARBON FIBER

M35J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan.

### PRODUCT DESIGNATION

M35J	B	12,000	5	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength 6K	654 ksi	4,510 MPa	TY-030B-01
Tensile Strength 12K	683 ksi	4,700 MPa	TY-030B-01
Tensile Modulus	49.8 Msi	343 GPa	TY-030B-01
Strain at Failure 6K		1.3%	TY-030B-01
Strain at Failure 12K		1.4%	TY-030B-01
Density		1.75 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	225 g/1000m	TY-030B-03
	12K	450 g /1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.73 α · 10 <sup>-6</sup> /°C
Specific Heat	0.723 J/g · °C
Thermal Conductivity	0.389 J/cm · s · °C
Electric Resistivity	1.1 x 10 <sup>-2</sup> Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	390 ksi	2,690 MPa	ASTM D-3039
Tensile Modulus*	29 Msi	202 GPa	ASTM D-3039
Tensile Strain		1.35%	ASTM D-3039
Compressive Strength*	203 ksi	1,400 MPa	SACMASRM1R-94
Flexural Strength*	239 ksi	1,650 MPa	ASTM D-790
Flexural Modulus*	25 Msi	169 GPa	ASTM D-790
ILSS	12 ksi	83.6 MPa	SACMASRM1R-94
In Plain Shear Strength	19 ksi	131 MPa	ASTM D-3518
90° Tensile Strength	10 ksi	68 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2592 epoxy at 130 °C.



## M35J

M35J Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	1.0	II	76	82	192	126	156	12	12
12K	2.0	II	76	82	192	157	156	12	24

**Bobbin Type:**

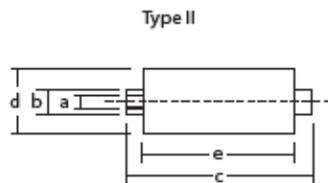

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

M35J Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# M40J

## HIGH MODULUS CARBON FIBER

M40J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan and France.

### PRODUCT DESIGNATION

M40J	B	12,000	5	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	640 ksi	4,400 MPa	TY-030B-01
Tensile Modulus	54.7 Msi	377 GPa	TY-030B-01
Strain at Failure		1.2%	TY-030B-01
Density		1.77 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	225 g /1000m	TY-030B-03
	12K	450 g /1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.83 α · 10 <sup>-6</sup> /°C
Specific Heat	0.723 J/g · °C
Thermal Conductivity	0.669 J/cm · s · °C
Electric Resistivity	1.0 x 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	363 ksi	2,500 MPa	ASTM D-3039
Tensile Modulus*	33 Msi	226 GPa	ASTM D-3039
Tensile Strain		1.11%	ASTM D-3039
Compressive Strength*	184 ksi	1,270 MPa	SACMASRM1R-94
Flexural Strength*	226 ksi	1,560 MPa	ASTM D-790
Flexural Modulus*	28 Msi	190 GPa	ASTM D-790
ILSS	12 ksi	83.1 MPa	SACMASRM1R-94
In Plain Shear Strength	18 ksi	123 MPa	ASTM D-3518
90° Tensile Strength	9 ksi	63 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2592 epoxy at 130 °C.



## M40J

M40J Rev. 1: Updated April 13, 2018



www.toraycma.com  
253-846-1777


**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	1.0	II	76	82	192	126	156	12	12
12K	2.0	II	76	82	192	157	156	12	24

**Bobbin Type:**

Type II

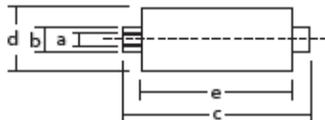

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

M40J Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# M46J

## HIGH MODULUS CARBON FIBER

M46J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan and France.

### PRODUCT DESIGNATION

M46J	B	12,000	5	O	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength 6K	609 ksi	4,200 MPa	TY-030B-01
Tensile Strength 12K	583 ksi	4,020 MPa	TY-030B-01
Tensile Modulus	63.3 Msi	436 GPa	TY-030B-01
Strain at Failure 6K		1.0%	TY-030B-01
Strain at Failure 12K		0.9%	TY-030B-01
Density		1.84 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	223 g/1000m	TY-030B-03
	12K	445 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-0.9 α · 10 <sup>-6</sup> /°C
Specific Heat	0.719 J/g · °C
Thermal Conductivity	0.836 J/cm · s · °C
Electric Resistivity	0.9 × 10 <sup>-2</sup> Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES\*

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	318 Ksi	2,190 MPa	ASTM D-3039
Tensile Modulus*	39 Msi	267 GPa	ASTM D-3039
Tensile Strain		0.83%	ASTM D-3039
Compressive Strength*	158 ksi	1,090 MPa	SACMASRM1R-94
Flexural Strength*	206 ksi	1,420 MPa	ASTM D-790
Flexural Modulus*	32 Msi	222 GPa	ASTM D-790
ILSS	12 ksi	82.8 MPa	SACMASRM1R-94
In Plain Shear Strength	11 ksi	77 MPa	ASTM D-3518
90° Tensile Strength	7 ksi	48 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.



## M46J

M46J Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	1.0	II	76	82	192	126	156	12	12
12K	2.0	II	76	82	192	157	156	12	24

**Bobbin Type:**

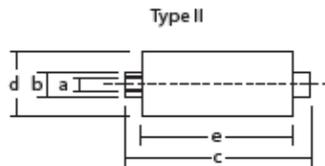

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed here in are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

M46J Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# M55J

## HIGH MODULUS CARBON FIBER

M55J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan.

### PRODUCT DESIGNATION

M55J	B	6,000	5	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	583 ksi	4,020 MPa	TY-030B-01
Tensile Modulus	78.2 Msi	540 GPa	TY-030B-01
Strain at Failure		0.8%	TY-030B-01
Density		1.91 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	6K	218 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-1.1 α · 10 <sup>-4</sup> /°C
Specific Heat	0.732 J/g · °C
Thermal Conductivity	0.961 J/cm · s · °C
Electric Resistivity	0.8 × 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.0%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	293 ksi	2,020 MPa	ASTM D-3039
Tensile Modulus*	49 Msi	338 GPa	ASTM D-3039
Tensile Strain		0.61%	ASTM D-3039
Compressive Strength*	129 ksi	890 MPa	SACMASRM1R-94
Flexural Strength*	171 ksi	1,180 MPa	ASTM D-790
Flexural Modulus*	40 Msi	274 GPa	ASTM D-790
ILSS	11 ksi	73.2 MPa	SACMASRM1R-94
In Plain Shear Strength	10 ksi	68 MPa	ASTM D-3518
90° Tensile Strength	5 ksi	37 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.



## M55J

M55J Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
6K	0.5	II	76	82	192	107	156	24	12

**Bobbin Type:**

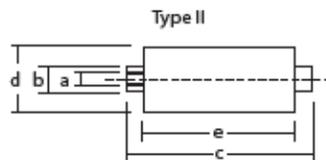

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

M55J Rev. 1: Updated April 13, 2018



Toray Composite Materials America, Inc.

# M60J

## HIGH MODULUS CARBON FIBER

M60J carbon fiber is an MJ-type high modulus fiber with enhanced tensile and compressive strength as compared to M series fibers. Manufactured in Japan.

### PRODUCT DESIGNATION

M60J	B	6,000	5	0	B
Fiber Type	Twist*	Filament Count	Sizing Type	Surface Treatment	Sizing Amount

\* B: Untwisted

### FIBER PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength	554 ksi	3,820 MPa	TY-030B-01
Tensile Modulus	85.3 Msi	588 GPa	TY-030B-01
Strain at Failure		0.7%	TY-030B-01
Density		1.93 g/cm <sup>3</sup>	TY-030B-02
Filament Diameter		5 μm	
Yield	3K	103 g/1000m	TY-030B-03
	6K	206 g/1000m	TY-030B-03

### FUNCTIONAL PROPERTIES

PROPERTY	VALUE
CTE	-1.1 α · 10 <sup>-6</sup> /°C
Specific Heat	0.732 J/g · °C
Thermal Conductivity	1.505 J/cm · s · °C
Electric Resistivity	0.7 × 10 <sup>-3</sup> Ω · cm
Chemical Composition: Carbon	>99%
Na + K	<50 ppm

### RESIN SYSTEM COMPATIBILITY

SIZING TYPE & AMOUNT	RESIN SYSTEM COMPATIBILITY	METHOD
50B (1.5%)	Epoxy, phenolic, polyester, vinyl ester	TY-030B-05

### COMPOSITE PROPERTIES

PROPERTY	ENGLISH	METRIC	METHOD
Tensile Strength*	292 ksi	2,010 MPa	ASTM D-3039
Tensile Modulus*	52 Msi	360 GPa	ASTM D-3039
Tensile Strain		0.55%	ASTM D-3039
Compressive Strength*	115 ksi	790 MPa	SACMASRM1R-94
Flexural Strength*	155 ksi	1,070 MPa	ASTM D-790
Flexural Modulus*	44 Msi	301 GPa	ASTM D-790
ILSS	10 ksi	70.3 MPa	SACMASRM1R-94
In Plain Shear Strength	8 ksi	55 MPa	ASTM D-3518
90° Tensile Strength	5 ksi	34 MPa	ASTM D-3039

\*Normalized to 60% fiber volume. Cured with #2500 epoxy at 130 °C.



## M60J

M60J Rev. 1: Updated April 13, 2018




www.toraycma.com  
253-846-1777

**PACKAGING**

The table below summarizes the tow sizes, twists, sizing types, and packaging available for standard material. Other bobbin sizes may be available on a limited basis.

TOW SIZES	BOBBIN NET WEIGHT (kg)	BOBBIN TYPE	BOBBIN SIZE (mm)					SPOOL PER CASE	CASE NET WEIGHT (kg)
			a	b	c	d	e		
3K	0.25	II	76	82	192	94	156	20	5
6K	0.4	II	76	82	192	103	156	20	8

**Bobbin Type:**

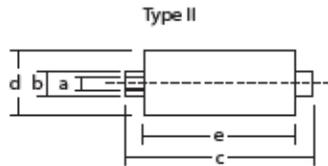

Please refer to SDS for handling and disposal.

**For more information or purchasing inquiries:**  
[sales@toraycma.com](mailto:sales@toraycma.com) | [www.toraycma.com](http://www.toraycma.com) | 253-846-1777

*The data listed herein are lot averages and for reference purposes only. The results are not intended for specification purposes. These commodities, technology or software were exported from the United States in accordance with the Export Administration Regulations. Diversion contrary to U.S. law is prohibited.*

M60J Rev. 1: Updated April 13, 2018